



---

## **ANALYSIS OF COMPOSITE SINGLE LAPJOINT UNDER TENSILE LOAD AT VARYING DESIGN CONDITIONS**

**CH V K N S N Moorthy**

Institute of Aeronautical Engineering, Hyderabad, India

**M Prashanth Reddy**

Institute of Aeronautical Engineering, Hyderabad, India

**Vankayala Jagadeshwar Babu**

Institute of Aeronautical Engineering, Hyderabad, India

**Ayyagari Kiran Kumar**

Dhanekula Institute of engineering and Technology, Vijayawada, India,

**V Srinivas**

GITAM Institute of Technology, GITAM University, Vishakhapatnam, India

**K Ramaswamy**

ASL, DRDO, Hyderabad, India

### **ABSTRACT**

*Composite materials have made way to several different fields, including aerospace structures, under water vehicles, automobiles and robot systems etc. Due to the high strength they are widely used in the low weight constructions and also used as a suitable alternative to metals. ANSYS FEA tool has been used for stress distribution characteristics of single lap joint with crack in-built in adhesive layer. In several different applications and also for joining various composite parts together, by using epoxy adhesives. Modeling and static analysis of 3D Models of lap joints were carried out and compared for two different composite materials. The present study deals with the analysis of single lap joint subjected to tensile load and the stress distribution in the joint members under various design conditions are to be found. The fracture characteristics of single-lap bonded joints in composites to be investigated by structural analysis. The failure process, failure mode and the behavior of load-displacement curve was apparently different according to bonding method to be evaluated.*

**Key words:** Composite Lap joint, adhesive layer, fracture characteristics, Adhesive joint Analysis etc.

**Cite this Article:** CH V K N S N Moorthy, M Prashanth Reddy, Vankayala Jagadeshwar Babu, Ayyagari Kiran Kumar, V Srinivas and K Ramaswamy, Analysis of Composite Single Lapjoint Under Tensile Load at Varying Design Conditions, International Journal of Mechanical Engineering and Technology, 10(02), 2019, pp. 1000–1010  
<http://www.iaeme.com/IJMET/issues.asp?JType=IJMET&VType=10&IType=02>

## 1. INTRODUCTION

A composite is a structural material that consists of two or more combined constituents that are combined at a macroscopic level and are not soluble in each other. Most commonly, composite materials have a bulk phase, which is continuous, called the matrix, and one dispersed, non-continuous, phase called the reinforcement. The reinforcing phase material may be in the form of fibers, particles, or flakes. The matrix phase materials are generally continuous. Examples of composite systems include concrete reinforced with steel and epoxy reinforced with graphite fibers, etc. The example of composite material is given in Fig.1.



Figure.1: Composite Material

### 1.1. Classification of Composites

Composites are classified based on:

1. Geometry of the reinforcement
2. Type of matrix

Based on the geometry of the reinforcement composites are classified into Particulate, Flake and Fibers.

Based on the type of matrix —

1. Polymer matrix
2. Metal matrix
3. Ceramic matrix

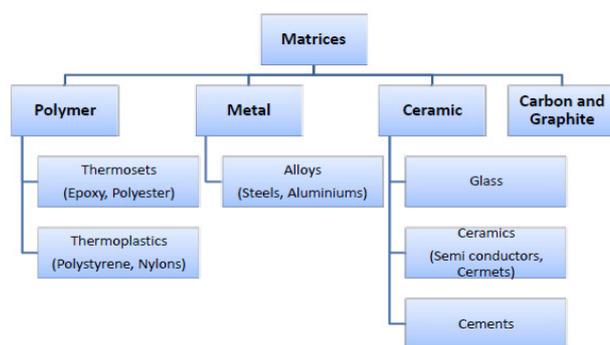


Figure.2: Classification of composites


### 1.2. Types of Composite Joints

There are two types of joints in FRP composites: - Adhesive joints (Permanent Joint) and Mechanical joints (Temporary Joint). These two types of joining are generally independent from each other but some time combined in a product to get additional benefit. Adhesive bonding is the most common type of joint used in composites joining. In adhesive bonding, two substrate

materials are joined by an adhesive. In mechanical joints, rivets bolts, and/or screws are used to form the joint.

**1.2.1. Adhesive Joints**


The adhesive joint is made between two substrate (Adherends) material with the help of an adhesive (e.g., epoxy, methyl acrylate cyanoacrylates, anaerobics, silicones, or phenolics). From the large variety of adhesives, the optimum selection of the adhesive material is very important. The selection of the adhesive material depends upon type of composites, applications, the service environment and the most importantly the cost. The adhesive materials are classified as: structural, pressure sensitive, hot melt, water based and radiation cured. Structural adhesives are the most commonly used when joining of fiber reinforced composites is required. Various types of adhesive joints (Fig. 3) are made with the help of adhesive bonding, for example, single lap, tapered lap, scarf, butt, strap, double strap, tapered double strap, double lap and stepped lap.[6-9]

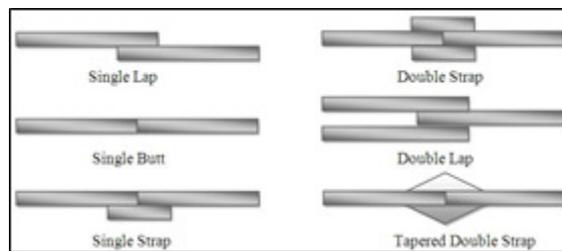

**Figure.3:** Types of Adhesive Joints

**2.1.2. Mechanical Joints**

Mechanical joints are made in fiber reinforced plastics composites by drilling a hole and placing a mechanical fastener between two joining members. Examples for mechanical joints are bolting, riveting, screw and pin joints. For most of the mechanical joints, an overlap is required in two mating members. The mechanical joints can be a single lap joint, double lap joint or butt joint.

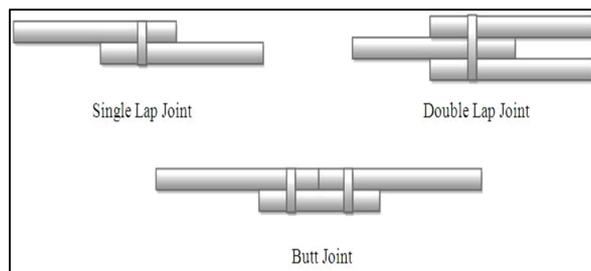

**Figure.4:** Various types of Mechanical Joints

**1.3. Types of failures for a laminate**


A laminate will fail while increasing the thermal and mechanical loads, however, may not be catastrophic. Failure modes are determined by the quality of the bond at each interface, specimen geometry and loading. They must be characterized to gain a full understanding of the properties of the adhesive and the joint being investigated. Fig.5 (MD Banea and LFMda Silva, 2008).[1-5 &10]. It is possible that some layer fails first and that the composite continues to take more loads until all the plies fail. Failed plies may still contribute to the stiffness and strength of the laminate.



**Figure.5:** Types of Failure modes of Laminate

## 2. DESIGN OF COMPOSITE LAP JOINT

Joining of fiber reinforced composites (FRPs) leads to a new dimension of concern among the researcher. The joining becomes an imperative and necessary domain to join individually processed composite parts into a usable assembly. Joining of FRP composites seems to be simple but it is much more than that. The design of joint in FRP composites is a very critical issue. The joint is a source of stress concentration and improper design may lead to increase in stress concentration and may become a cause of failure during in service of the product. Joint add manufacturing depending time and labor cost to the product. Different joining methods can be used upon the complexity of the structure or product and its application area considering. Fig.6. [11-15].

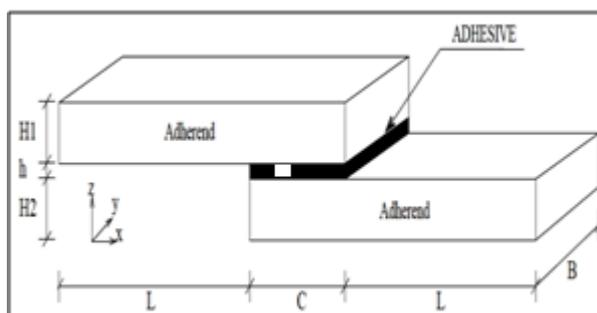

**Figure.6:** Design of composite lap joint with inbuilt crack


The following conditions should satisfy Design of a joint

1. Allowable shear stress and tensile stress of adhesive should not exceeded
2. Allowable in-plane shear stress and through-thickness tensile stress of adherend should not exceeded

For maximising the static strength and fatigue performance of adhesively bonded joints include (NPL Manual, 2007), [46-51]

- Minimise shear and peel stress concentrations - shear and peel stress concentrations present at bondline ends can be minimized by using the tapered or bevelled external scarf or radiused adhesive fillets. Significant increases in the joint strength compared with square-ended bondlines can be achieved
- Increasing either the adherend stiffness or adherend thickness results in an increase in load-carrying capacity of the single-lap joint. The use of stiff or thick adherends will reduce peak stress levels and which promotes more uniform adhesive stress distribution. By using the absolutely rigid adherend will not prevent the formation of stress concentration at the ends. The overlap length must be long to ensure that the shear stress in the middle of the overlap is low to avoid creep. Short overlaps result in failure through creep-rupture. In order to have a uniform shear stress distribution the overlap length must be 10 times of adhesive thickness.[16]

- the joint must be loaded in the direction of maximum strength of the adherend. The bonded joint needs not only to be loaded in the direction of maximum strength, but also loads in the weak directions need to be minimised.
- Bond must have a uniform thickness and it is recommended to join identical adherends to minimise skewing of the peak and normal stresses, and to reduce thermal residual stresses due to differences in coefficient of thermal expansion values.[17].
- interlaminar shear or tensile failures of composite adherends is avoided. Also, ensure the laminated adherend must be symmetric, which ensures the coupling stiffness components of the laminate are zero (i.e. no twisting).[18-21].
- Account for differences in thermal expansion coefficients of the adhesive and adherends. This Difference can lead to bending stresses and residual stresses, which will decrease the joint performance.

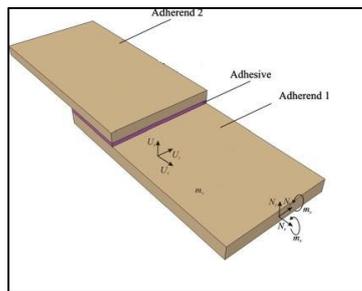

**Figure.7:** Configuration of composite Lap Joint

## 2.1. MATERIAL SELECTION

Carbon fibers have high strengths and low densities and so are used in many applications, particularly aerospace, in spite of their higher cost. Fiber reinforced plastic composites are superior to metals in terms of specific strength and stiffness, corrosion resistance, and formability. Composite materials, therefore, are used for primary structures of small or mid-sized nautical vessels, and aerospace structures.

## 2.2. Adhesive properties

Most of the industries are demanding new adhesive materials with advanced properties which should satisfy the required conditions for a specific application. In order to meet the necessary requirements, new adhesive materials are developed with more advanced properties.

## 2.3. Design of Composite Adhered

Although, there are numerous adhesive materials available in the market, selection of adhesive materials for a specific application is not an easy task as it depends on many factors (i.e. adherend type to be bonded, curing temperature, expected environmental condition during service, type of load, cost etc.).[22-27] Nowadays, the extensive application of adhesive bonding in the industry is a positive step, but reuse, recycling and recovery of bonded parts are the major concerns mainly because of environmental issues. To overcome this, the adhesive bonding should easily dis-bond without damaging the structure.

- Araldite AW-106
- Hardener – HV953U

Considered the carbon epoxy composite plate for adhered and ply sequence is given, and configuration is given [30]

S.No	Layer type	Orientation (°)	Thickness (mm)
1	Hoop	0	0.40
2	Helical	45	0.40
3	Helical	45	0.40
4	Hoop	0	0.40

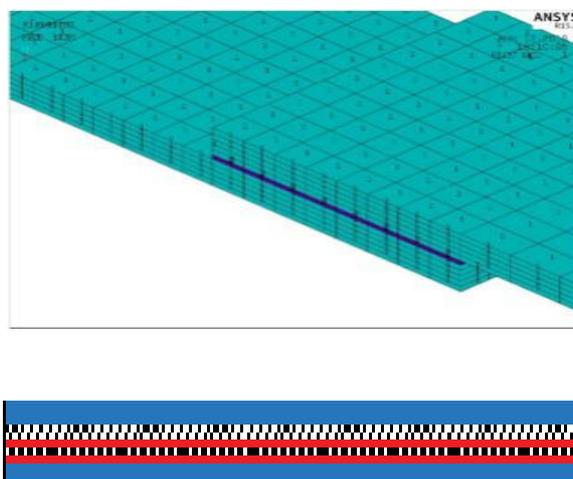


Figure.8: Ply Sequence of composite Adhered

## 2.4. Stress Calculations for Composite Lap Joint

The ply design and the stresses, loads calculations are carried out based on the classical laminate theory (CLT). [34] The details of CLT [2] as follows:

Properties for Carbon fiber T-700:

$E_1 = 117\text{GPa}$ ;  $E_2 = 8\text{GPa}$ ;  $\nu = 0.3$ .

$$\begin{bmatrix} \sigma_x \\ \sigma_y \\ \tau_{xy} \end{bmatrix} = \begin{bmatrix} \bar{Q}_{11} & \bar{Q}_{12} & \bar{Q}_{16} \\ \bar{Q}_{12} & \bar{Q}_{22} & \bar{Q}_{26} \\ \bar{Q}_{16} & \bar{Q}_{26} & \bar{Q}_{66} \end{bmatrix} \begin{bmatrix} \epsilon_x \\ \epsilon_y \\ \gamma_{xy} \end{bmatrix}$$

1

Step-1: Calculate the stiffness matrix based on the engineering constants:

$$Q = \begin{bmatrix} Q_{11} & Q_{12} & 0 \\ Q_{12} & Q_{22} & 0 \\ 0 & 0 & Q_{66} \end{bmatrix}$$

2

$$\frac{\nu_{ij}}{E_i} = \frac{\nu_{ji}}{E_j}$$

$$Q_{11} = \frac{E_1}{1 - \nu_{12}\nu_{21}} \quad Q_{12} = \frac{\nu_{12}E_2}{1 - \nu_{12}\nu_{21}} \quad Q_{22} = \frac{E_2}{1 - \nu_{12}\nu_{21}} \quad Q_{66} = G_{12} \quad Q_{13} = Q_{21}$$


3

Stresses are within the strength of composite materials and CE plates are safe during testing of lap joint. The fiber orientation 30° and 45° are very close in transverse tensile stress and manufacturing point of view, 45° fiber is selected along with 0° fiber orientation.

### 3.5. FEA Elements

- Define element type to Quadrants and nodes.
- Create key points to form areas of rectangles.
- Define material properties for each area Glue the areas together to represent adhesion.
- Create mesh with a minimum of 10 elements.
- Define loads and fixed points.
- Generate solution and contour plots.

The numbers of FEA elements are used for analysis of joint. The finite element mesh is generated using a three-dimensional brick element ‘SOLID45’. (ANSYS R15.0).[28 & 29] This element is a structural solid element designed based on three-dimensional elasticity theory and is used to model thick orthotropic solids. The element is defined by 8 nodes having three degrees of freedom per node: translations in the nodal x, y, and z direct.

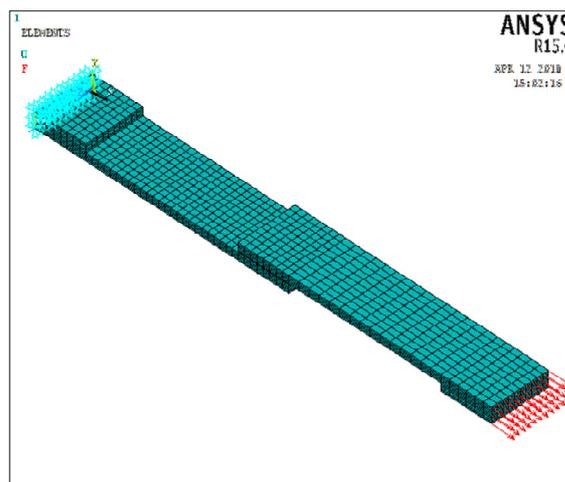

The  $U_x = 0, U_y=0$  and  $U_z=0$

**Figure.9:** Loads and Boundary Conditions

The boundary conditions applied in this composite plate is one end is fixed and other end the load is applied as shown in fig.9.

[30-33] FEA analysis of adhesive joint gives some important observations which are given as below:

- In this type of joint the highest stress concentrations occurs (at the free ends of the joint).
- The centre of the joint transfer less loads.
- Tapered or bevelled external scarf or radiused adhesive fillets minimize the stress concentrations at the free ends of the joint.

### **3.6. Standard test method for Strength Properties of adhesives in Shear by Tension Loading of single Lap Joint Laminated Assemblies (As per ASTM Standards D3165)**

This test method (Note-1) is intended for determining the comparative shear strengths of adhesives in large area joints when tested on a standard single-lap-joint specimen and under specified conditions of preparation and testing. Adhesives respond differently in small versus large area joints.

The test method is useful in that the joint configuration closely simulates the actual joint configuration of many bonded assemblies. Surface preparation of the adherends can affect the apparent shear strength of the adhesive and can be one of the variables under study. [35–38] This test method is also useful as an in-process quality control test for laminated assemblies. Either in practice, the laminated assembly is made over size and test specimens removed from it or a percentage of the assemblies are destructively tested.

The misuse of strength values obtained from this test method as design allowable stress values for structural joints could lead to product failure. Property damage and human injury. The apparent shear strength of an adhesive obtained from a given small single-lap specimen may differ from that obtained from a joint made with different adherends or by a different bonding process. The normal variation of temperature and moisture in the service environment causes the adherends and the adhesive to swell and shrink. The adherends and adhesive are likely to have different thermal and moisture coefficients of expansion.

Even in small specimens, short-term environmental changes can induce internal stresses or chemical changes in the adhesive that permanently affect the apparent strength and other mechanical properties of the adhesive. The problem of predicting joint behavior in a changing environment is even more difficult if a different type of adherend is used in a larger structural joint than was used in the small specimen.

The apparent shear strength measured with a single-lap specimen is not suitable for determinate design allowable stresses for designing structural joints that differ in any manner from the joints tested without thorough analysis and understanding of the joint and adhesive behaviors.

Single-lap tests may be used for comparing and selecting adhesives or bonding processes for susceptibility to fatigue and environmental changes, but such comparisons must be made with great caution since different adhesives may respond differently in different joints. Review Guide D4896 for further discussion of concepts for interpretation of adhesive-bonded single-lap joint data.

## **4. CONCLUSION**

This study presented single lap adhesively bonded joint configurations that are employed in various applications. The main outcomes of this study are to understand joining of two composite plates using adhesive joint. In several different applications and also for joining various composite parts together, by using epoxy adhesives. Modeling and static analysis of 3D Models of lap joints were carried out and compared for two different composite materials. The present study deals with the analysis of single lap joint subjected to tensile load and the stress distribution in the joint members under various design conditions.

The overlap length is most important factor which affects adhesive strength, adhesive properties, adherend properties and joining procedure also. For the optimal overlap length the joint strength is maximum with minimum applied adhesive which increases load bearing capacity of joint. The most of problems in numerical analysis are addressed to mechanical properties of adhesive which are often publicly unknown. Accuracy of adhesive properties is influenced with

reliability of materials models. Parametric study on lap joints in FEA gives stress peaks at critical locations by a more refined FE mesh.

The fracture characteristics of single-lap bonded joints in composites to be investigated by structural analysis.

## REFERENCES:

- [1] Banea MD, da Silva LFM. Adhesively bonded joints in composite materials: an overview. *Proc IME J Mater Des Appl* 2009; 223:1–18.
- [2] CH V K N S N Moorthy, V Srinivas, “Discretization analysis of a composite GFRP cylinder”, *International Journal of Engineering and Technology*, Vol. 7, Issue. 4, 277-279, 2018.
- [3] Banea MD, da Silva LFM, Campilho RDSG, Sato C. Smart adhesive joints: an overview of recent developments. *J Adhes* 2014; 90:16–40.
- [4] Budhe S. Effect of pre-bond moisture on the static and fatigue behavior of bonded joints between CFRP laminates for structures repairs [PhD thesis]. Spain:University of Girona; 2014.
- [5] Bouchikhi AS, Megueni A, Gouasmi S, Boukoulou FB. Effect of mixed adhesive joints and tapered plate on stresses in retrofitted beams bonded with a fiber reinforced polymer plate. *Mater Des* 2013; 50:893–904.
- [6] Banea MD, da Silva LFM, Carbas RJC, de Barros S. Debonding on command of multi-material adhesive joints. *J Adhes* 2016.
- [7] CH V K N S N Moorthy, V Srinivas, “Discretization Analysis of a Composite GFRP Cylinder”, *International Conference on Recent Trends in Engineering and Sciences*, CPGC, India, 2018.
- [8] Cooper V, Ivankovic A, Karac A, McAuliffe D, Murphy N. Effects of bond gap thickness on the fracture of nano-toughened epoxy adhesive joints. *Polymer* 2013; 53:5540–53.
- [9] Davies P, Sohler L, Cognard JY, Bourmaud A, Choqueuse D, Rinnert E, Creac R. Influence of adhesive bond line thickness on joint strength. *Int J Adhes Adhes* 2009; 29:724–36.
- [10] Da Silva LFM, Ferreira NAMJ, Richter-Trummer V, Marques EAS. Effect of grooves on the strength of adhesively bonded joints. *Int J Adhes Adhes* 2010; 30:735–43.
- [11] G, Ouyang Z, Li G. Effects of bondline thickness on Mode-I nonlinear interfacial fracture of laminated composites: an experimental study. *Compos Part B-Eng* 2013; 47:1–7.
- [12] V. Srinivas, CH. V. K. N. S. N. Moorthy, V. Dedeepya and P. A. Thompson, “Water based nano fluids for automotive applications”, *Journal of Mechanical Science and Technology*, Korean Society of Mechanical Engineers, Springer 29 (8), 3417 - 3426, 2015.
- [13] Gültekin K, Akpınar S, Özel A. The effect of the adherend width on the strength of adhesively bonded single-lap joint: experimental and numerical analysis. *Compos Part B-Eng* 2014; 60:736–45.
- [14] He X. A review of finite element analysis of adhesively bonded joints. *Int J Adhes Adhes* 2011; 31:248–64.
- [15] Ji G, Ouyang Z, Li G, Ibekwe S, Pang SS. Effects of adhesive thickness on global and local Mode-I interfacial fracture of bonded joints. *Int J Solids Struct* 2010; 47:2445–58.
- [16] Jen YM, Ko CW. Evaluation of fatigue life of adhesively bonded aluminum single lap joints using interfacial parameters. *Int J Fatigue* 2010; 32:330–40.
- [17] Chellapilla V K N S N Moorthy, Vadapalli Srinivas, “Corrosion and Heat Transfer Characteristics of Water Dispersed with Carboxylate Additives & Multi-walled Carbon

- Nano Tubes,” *Journal of the Institution of Engineers (India): Series C*, Springer India, Vol. 97, and Issue. 4, 569-577, 2016.
- [18] Kanerva M, Saarela O. The peel ply surface treatment for adhesive bonding of composites: a review. *Int J Adhes Adhes* 2013;43:60–9.
- [19] Li J, Yan Y, Zhang T, Liang Z. Experimental study of adhesively bonded CFRP joints subjected to tensile loads. *Int J Adhes Adhes* 2015; 57:95–104.
- [20] Marzi S, Biel A, Stigh U. On experimental methods to investigate the effect of layer thickness on the fracture behavior of adhesively bonded joints. *Int J Adhes Adhes* 2011; 31:840–50.
- [21] CH V K N S N Moorthy, V Srinivas, “Relative Investigations of Various Parameters of Steel with a Composite GFRP Cylinder”, *International Conference on Recent Trends in Engineering and Sciences, CPGC, India*, 2018.
- [22] Marques EAS, Campilho RDSG, da Silva LFM. Geometrical study of mixed adhesive joints for high temperature applications. *J Adhes Sci Technol* 2016; 30:691–707.
- [23] Naito K, Onta M, Kogo Y. The effect of adhesive thickness on tensile and shear strength of polyimide adhesive. *Int J Adhes Adhes* 2012; 36:77–85.
- [24] Nanda Kishore A, Siva Prasad N. An experimental study of Flat-Joggle-Flat bonded joints in composite laminates. *Int J Adhes Adhes* 2012; 35:55–8.
- [25] Ozel A, Yazici B, Akpınar S, Aydin MD, Temiz S. A study on the strength of adhesively bonded joints with different adherends. *Compos Part B-Eng* 2014; 62:167–74.
- [26] Park YB, Song MG, Kim JJ, Kweon JH, Choi JH. Strength of carbon/epoxy composite single-lap bonded joints in various environmental conditions. *Compos Struct* 2010; 92:2173–80.
- [27] Palmieri FL, Belcher MA, Wohl CJ, Blohowiak KY, Connell JW. Laser ablation surface preparation for adhesive bonding of carbon fiber reinforced epoxy composites. *Int J Adhes Adhes* 2016; 68:95–101.
- [28] M. Ashok Kumar, K. Deepak, CH. V. K. N. S. N. Moorthy, B. Subramanyam, “Influence of Fiber Orientation on the Properties of Composites”, *International Journal of Mechanical and Production Engineering Research and Development*, Vol. 8, Issue. 1, 487-494, 2018.
- [29] P. Maimi, P.P. Camanho, J.A. Mayugo, C.G. Davila, (2007), A continuum damage model for composite laminates: Part I – Constitutive model, *Mechanics of Materials* 39 (2007) pp 897–908.
- [30] P. Maimi, P.P. Camanho, J.A. Mayugo, C.G. Davila, (2007), A continuum damage model for composite laminates: Part II – Computational implementation and Validation, *Mechanics of Materials* 39, pp 909–919
- [31] Pradhan, B. and Chakraborty, D. (2000), Fracture Behavior of FRP Composite Laminates with Embedded Elliptical Delaminations at the Interface, *Journal of Reinforced Plastics & Composites*, 19(13), pp 1004–1023.
- [32] Pradhan, B. and Panda, S.K., (2006), The Influence of p-Seq and Thermo elastic Stress Field on Asymmetric Delamination Crack Growth Behavior of Embedded Elliptical Delaminations in Laminated FRP Composites, *Composites Science and Technology*, 36(3–4), pp 417–426.
- [33] CH V K N S N Moorthy, V Srinivas, “Stress Analysis of Domestic Composite LPG Cylinder Using Classical Lamination Theory (CLT), *International Journal of Engineering and Technology*, Vol. 7, Issue. 4, 68-70, 2018.
- [34] Ronald Krueger, *Computational Fracture Mechanics for Composites, State of the art and challenges*, (2006), Presented at the NAFEMS Nordic Seminar: Prediction and Modeling of Failure Using FEA, Copenhagen/Roskilde, Denmark.
- [35] Reis PNB, Ferreira JAM, Antunes F. Effect of adherend’s rigidity on the shear strength of single lap adhesive joints. *Int J Adhes Adhes* 2011; 31:193–201.

- [36] CH V K N S N Moorthy, V Srinivas, “Design and Development of a Composite Ply for a GFRP Cylinder”, International Conference on Recent Trends in Engineering and Sciences, CPGC, India, 2018.
- [37] Song MG, Kweon JH, Choi JH, Byun JH, Song MH, Shin SJ, Lee J. Effect of manufacturing methods on the shear strength of composite single-lap bonded joints. *Compos Struct* 2010; 92:2194–202.
- [38] Sinmazçelik T, Avcu E, Bora MO, Çoban O. A review: fibre metal laminates, background, bonding types and applied test methods. *Mater Des* 2011; 32:3671–85.
- [39] Sun, C. T. and Jih.C. J., (1987), On Strain Energy Release Rates for Interfacial Crack in BiMaterial Media, *Engineering Fracture Mechanics*, 28(1), pp 13–20.
- [40] Ayyagari Kiran Kumar, V. Srinivas, Ch.V.K.N.S.N. Murthy, “Modelling and Performance Analysis of Aero Piston Engine”, *Journal of Advanced Research in Dynamical and Control Systems*, Vol. 10, Issue 7, 344-348, 2018.
- [41] Sun.C.T. and Manoharan.M.G, (1989), Strain Energy Release Rates of an Interfacial Crack between Two Orthotropic Solids, *Journal of Composite Materials*, 23, pp 460– 478.
- [42] S. K. Panigrahi and B. Pradhan, (2007), Three Dimensional Failure Analysis and Damage Propagation Behavior of Adhesively Bonded Single Lap Joints in Laminated FRP Composites, *Journal of Reinforced Plastics and Composites* 26, 183201.
- [43] V. Srinivas, Ch. V. K. N. S. N. Moorthy, V. Dedeepya, P. V. Manikanta, V. Satish, “Nanofluids with CNTs for automotive applications”, *Journal of Heat and Mass Transfer*, Springer Berlin Heidelberg, Springer 52(4), 701-712, 2016.
- [44] Tang JH, Sridhar I, Srikanth N. Static and fatigue failure analysis of adhesively bonded thick composite single lap joints. *Compos Sci Technol* 2013;86:18–25.
- [45] Yuval Freed, Leslie Banks Sills, (2008), A new cohesive zone model for mixed mode interface fracture in bimetals, *Engineering Fracture Mechanics* 75 , pp 4583–4593.
- [46] Fibre reinforced composites by P.K.Mallick
- [47] Handbook of composites by Sotiris Koussis
- [48] A study of fibrous composite material by Federico Paris
- [49] Ultimate behavior of adhesively bonded FRP lap joint by Francesco Ascione
- [50] Effects of geometric and material parameters on strength of composite joints by Jacod I. Rome
- [51] Fracture behavior in CFRP cross-ply laminate with initially cut fiber by S.Yashiro, K.Oggi